

ADVANCES IN SUSTAINABLE CONCRETE THROUGH INDUSTRIAL WASTE UTILIZATION AND NANOTECHNOLOGY

Muhammad Zakir Arfat^{*1}, Qasim Masood², Usman Fiaz³, Huda Riaz⁴, Haseeb Ahmad⁵

^{*1}The Urban Solutions (Pvt.) LTD, Islamabad,

²Institute of Geology, University of the Punjab, new campus,

³Project management, Infrastructure development authority Punjab,

⁴UET, Faculty of engineering, Department of architectural engineering, Lahore, 54792, Pakistan,

⁵Civil Engineering technology, UOL, Lahore, Pakistan

^{*1}zakirarfath313@gmail.com , ²qasim.res.geo@pu.edu.pk, ³usmanfiaz333@gmail.com,

⁴hriaz45@gmail.com

DOI: <https://doi.org/10.5281/zenodo.21126989>

Keywords

Sustainable Concrete, Industrial Waste, Waste Glass Powder, Waste Marble Powder, Silica Fumes, Sustainable Environment, Waste Management, Nanotechnology

Article History

Received: 28 March 2026

Accepted: 07 May 2026

Published: 25 May 2026

Copyright @Author

Corresponding Author: *

Muhammad Zakir Arfat

Abstract

Concrete is the building industry's most widely used commodity that is blamed for some of the pollution issues around the world. So by replacing concrete ingredients, it can theoretically conserve natural resources and production of cement, reduce energy consumption, and remove small landfill areas of excessive waste production. Therefore, this research focuses on the behavior of industrial solid waste materials (waste glass powder, waste marble powder, silica fumes, fly ash, E-waste, blast furnace slag, pumic and nano materials) as replacement of concrete ingredients. It not only resolve the problem of landfill but also enhances the concrete properties. Green concrete manufacturing can be improved by using nanotechnology as it studies the behavior of material at atomic scale 10^{-9} . The methodology involves a comprehensive analysis of life cycle assessment studies, country-specific waste material production, and concrete performance focusing on environmental impacts and physical properties. This review is beneficial for construction industry and researchers to identify new material for sustainable construction.

INTRODUCTION

Due to factors like the partial substitution of waste items for cement, the avoidance of waste disposal expenditures, the reduction of production energy consumption, and the increased durability, green or sustainable concrete is frequently also less expensive to create. Green concrete is a type of concrete that looks like regular concrete but uses less energy and has less of an adverse environmental impact during manufacturing or use. For every tonne of

concrete produced, the CO₂ emissions associated with this process range from 0.1 to 0.22 tons [1, 34]. When clays and limestone are crushed and heated to high temperatures, the greenhouse gas is emitted [2, 35].

Waste usage is preferable to disposal since it reduces or even eliminates disposal expenses and related environmental problems while conserving resources. From a variety of angles, such as the conservation and recycling of energy in manufacturing processes, the preservation and

sustainability of nonrenewable natural resources, and the mitigation of pollution, trash reuse is essential [3,4]. Many types of "green concrete" are being created in response to the increasing demand to lessen the negative effects of the building sector, conserve raw materials, and avoid the disposal of industrial waste [4, 49]. The waste products from industry, agriculture, bio-waste, marine debris, and e-waste can all be recycled and utilized as additional components for Green Concrete. This will lessen the energy usage and environmental impact of OPC production. Both now and in the future, nanotechnology will play a huge role in green building applications. Green Concrete's development and application are still in their early phases [5, 38].

The manufacture of nanomaterials is still done on a lab scale, tends to be very energy intensive, and is not fully optimized. Although the use of nanomaterials in concrete is growing, there are still few studies on their effects on the environment or their possible ecotoxicity and toxicity (for example, from a safe and sustainable-by-design perspective) and further research is needed [6, 39]. Concrete is currently utilizing nanotechnology. By increasing the materials' lifespan, both organic and inorganic species can be employed as nano agents to create materials with better qualities, resulting in financial and environmental benefits [7, 47].

An enormous amount of waste materials from different surroundings, environments and industries are produced every day. The waste

materials such as rice husk ash (RHA), saw dust ash (SDA), rubber crump, plastic waste, coconut husk and shell, textile waste (sludge and fiber) etc lead to waste disposal crisis. Recycle of such types of wastes can be used as an admixture to make the Green Concrete structures. This will reduce the quantity of cement used and CO₂ emission and reduce the global warming. In this paper, the explanation is about the waste materials as an admixture which provides better strength and durability of concrete than the existing one which not only solves the environmental and ecological problems but also significantly improves the microstructures and durability properties of concrete. So this study summarizes the waste materials and nano materials along with its properties.

Methodology

Current research about green concrete and nanotechnology in concrete was studied to gather the necessary information that any unknowledgeable reader would need to comprehend the article. This study was conducted as a systematic literature review on the use of industrial solid waste materials in sustainable concrete production. The review focused on identifying the effects of different waste-based additives and nano-additives on the mechanical, durability, environmental, and microstructural properties of concrete. Below is the framework as figure 1.

METHODOLOGY FRAMEWORK

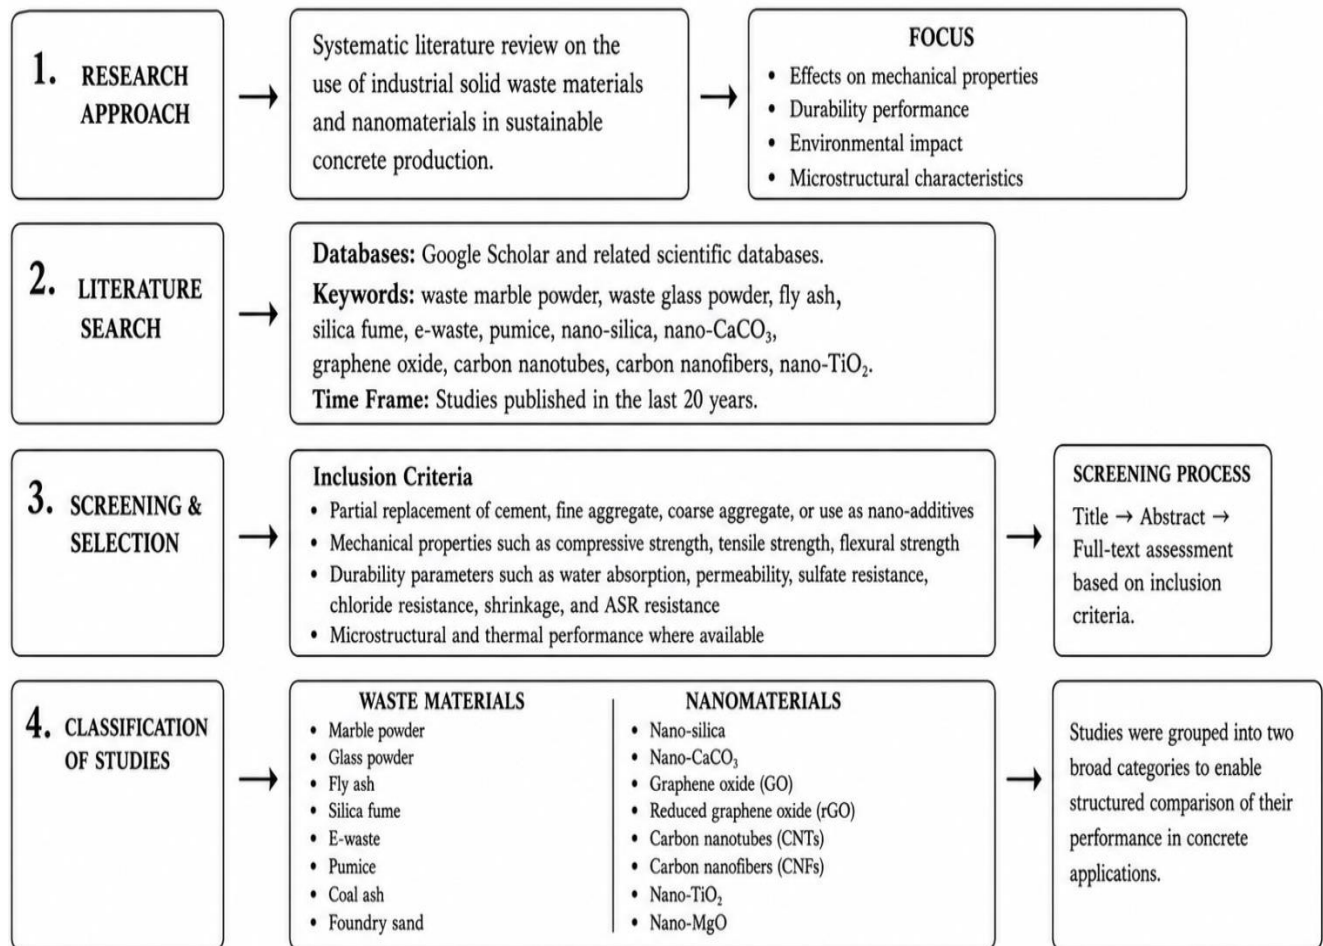


Figure 1: Methodological frame work

The literature search was carried out using Google Scholar and related scientific databases, with keywords such as industrial waste materials, nano materials, waste marble powder, waste glass powder, fly ash, silica fume, e-waste, pumice, nano-silica, nano-CaCO₃, graphene oxide, carbon nanotubes, carbon nano fibers, and nano-TiO₂. Studies published over the last 20 years were considered to ensure that the review captured both foundational and recent

developments in green concrete research. After screening, the selected studies were grouped into two broad categories: waste materials and nano materials. Waste materials included marble powder, glass powder, fly ash, silica fume, e-waste, pumice, coal ash, and foundry sand, while nano materials included nano-silica, nano-CaCO₃, graphene oxide, reduced graphene oxide, carbon nanotubes, carbon nano fibers, nano-TiO₂, and nano-MgO.



Figure 2: Year-wise publication trend of waste materials

The figure 2 illustrates the year-wise publication trend of waste material research in sustainable concrete from 2005 to 2025. In the initial years (2005–2008), the number of publications was relatively low, ranging from 1 to 2 publications per year, indicating the early stage of research on waste materials in concrete applications. From 2009 onwards, research activity gradually increased, with noticeable growth between 2010 and 2017, reflecting growing awareness of sustainable construction practices and waste utilization. A significant rise in publications was observed after 2016, with the number of studies reaching 9 publications in 2017 and again in 2019–2020. The highest publication output occurred in 2022 with 10 publications,

demonstrating peak global interest in incorporating waste materials such as marble powder, fly ash, silica fume, glass powder, coal ash, e-waste, pumice, and foundry sand into concrete production. Although the number of publications slightly declined after 2022, research activity remained relatively high through 2025, indicating the continued importance of waste-based sustainable concrete technologies. Overall, the graph highlights the increasing research focus on reducing environmental pollution, minimizing landfill disposal, and lowering cement consumption through the utilization of industrial and agricultural waste materials in concrete.

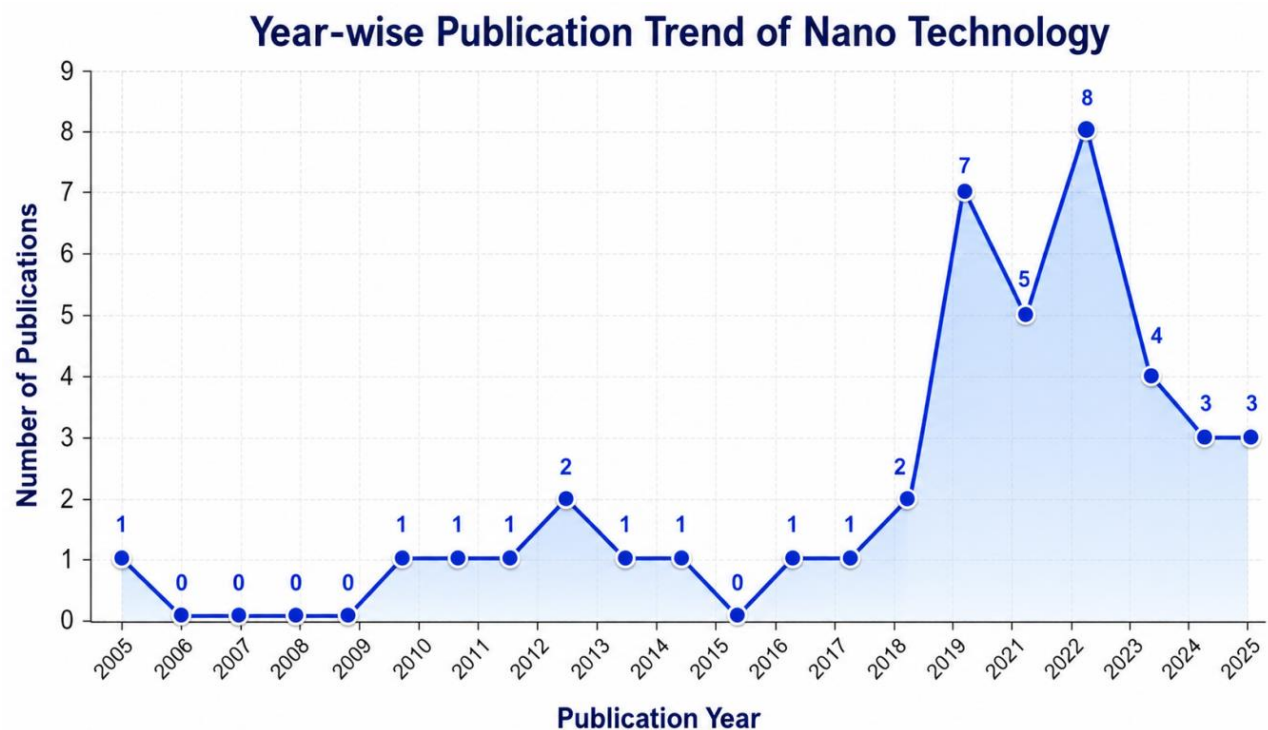


Figure 3: Year-wise publication trend of nano materials

The figure 3 illustrates the year-wise publication trend of nanotechnology research in sustainable concrete from 2005 to 2025. During the early years (2005–2018), the number of publications remained relatively low and inconsistent, generally ranging from 0 to 2 publications per year, indicating that nanotechnology applications in concrete were still at an emerging stage. However, a significant rise in research activity began after 2018, with publications increasing sharply from 2 in 2018 to 7 in 2019. Although a slight fluctuation occurred in 2021, the highest number of publications was recorded in 2022 with 8 publications, demonstrating peak research

interest in nanotechnology-based sustainable concrete. After 2022, the number of publications gradually declined but remained comparatively high between 2023 and 2025, indicating continued global interest in nano-engineered concrete materials. Overall, the graph highlights the rapidly growing importance of nanotechnology, including nano-silica, graphene oxide, carbon nanotubes, carbon nanofibers, and nano-metal oxides, in improving the mechanical, durability, and sustainability performance of concrete for advanced construction application. The flow chart in figure 4 explain the material and its significance

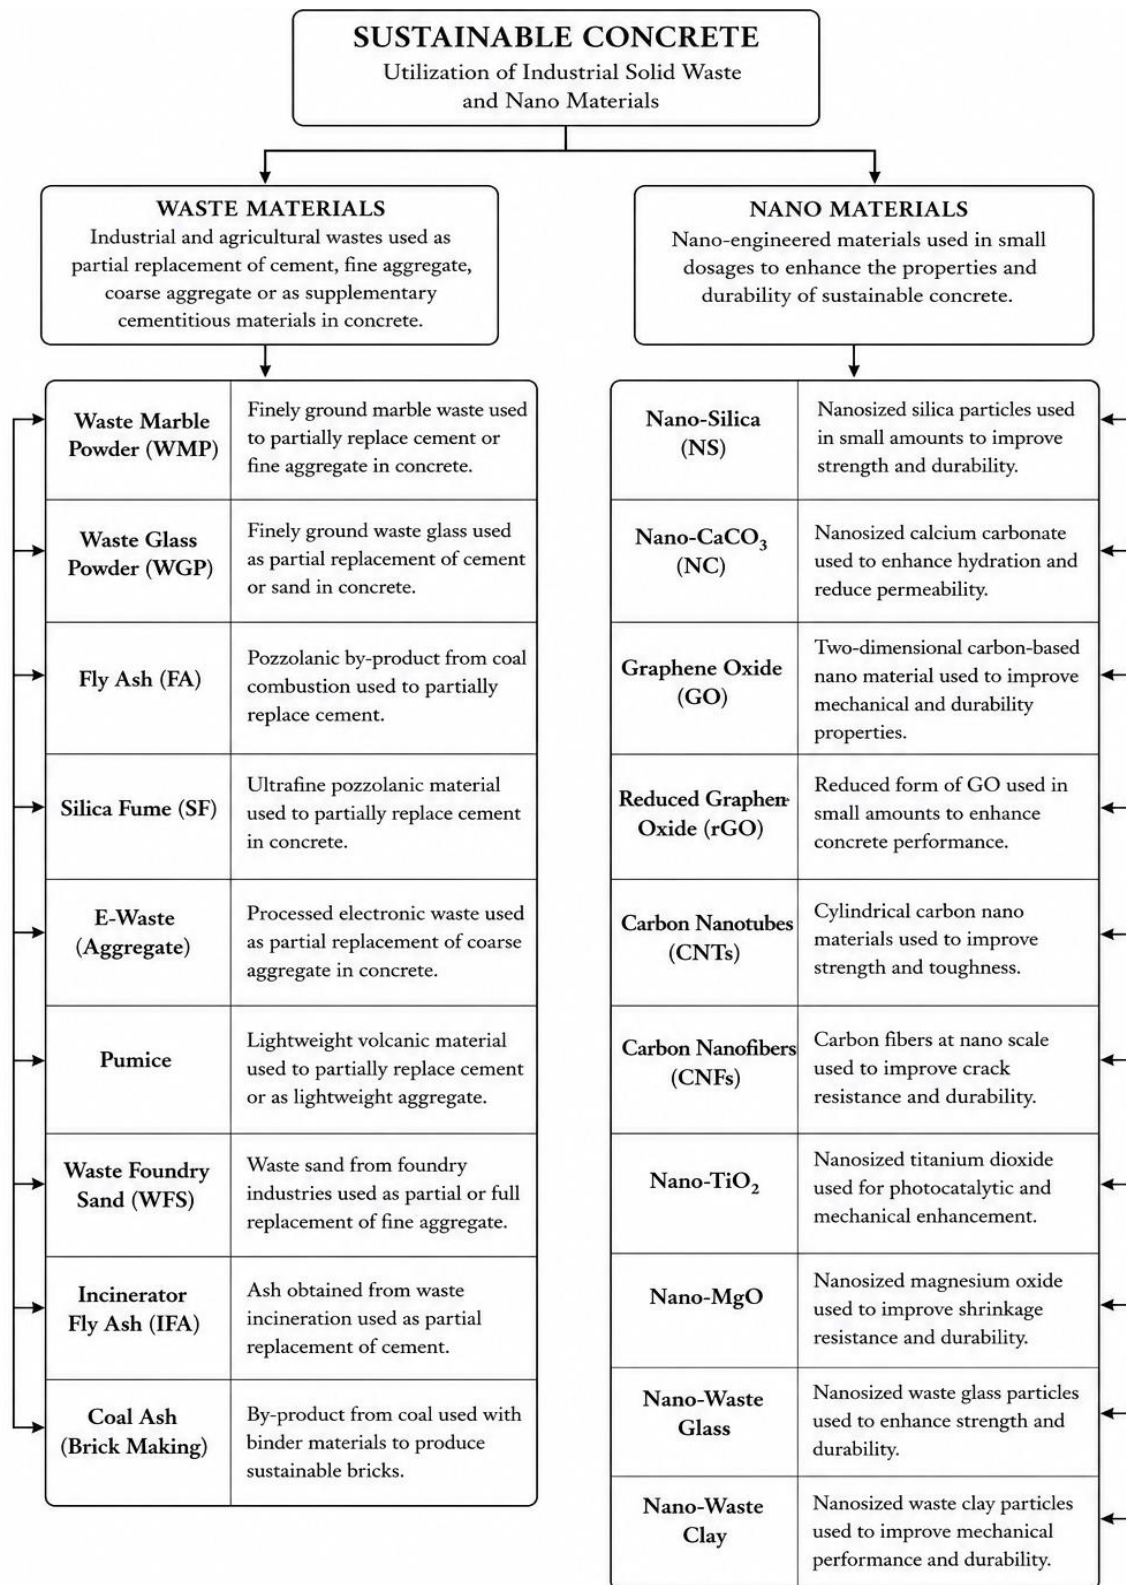


Figure 4: Flow chart of waste materials

Sustainable /green concrete**Waste marble powder**

According to Kishan et al. [1], replacing fine aggregates with up to 50% WMP increased compressive strength; however, greater percentages resulted in decreases. Similarly, Tayeh [2], Rai et al. [5], Tewodros Getachew et al. [15], Ofuyatan et al. [13], and Sonu Pal et al. [8] found that substituting powdered wastes, such as marble powder, for cement at levels of 10–30% led to a decrease in workability and a decrease in compressive strength. These results are in line with those of Abdul Ghani et al. [12], who discovered that mechanical qualities improved up to a specific percentage of WMP inclusion, with 40% sand replacement yielding the best compressive strength.

Studies show that when WMP content increases, workability trends consistently decline. According to Tayeh [2,11], Abdul Ghani et al. [12], and Sahil Patial and Sharma [10], higher WMP levels result in lower slump values and poorer workability, frequently because of increased surface area and water consumption. Despite this disadvantage, WMP has been shown to improve durability in a number of experiments. For instance, WMP can effectively reduce the alkali-silica reaction (ASR), enhancing long-term durability, according to Kishan et al. [1], while Abdul Ghani et al. [12] found that water permeability dropped as WMP content increased. Furthermore, Belouadah et al. [9] discovered that adding WMP decreased shrinkage, outperforming glass powder in this regard.

According to the literature, the ideal replacement amounts typically fall between 5–15% cement substitution and 25–40% fine aggregate substitution. Improvements in flexural, tensile, and compressive strengths are regularly noted at these levels [1, 8, 12, 13, 14, 15]. Both mechanical qualities and workability tend to decline beyond these limits.

All things considered, the reviewed research highlight the two advantages of WMP in concrete. By lowering waste disposal and preserving natural sand and cement resources, it improves specific mechanical and durability

qualities within the ideal replacement range and supports sustainable building [1, 9, 12].

The incorporation of waste marble powder (WMP) into concrete has been extensively explored to enhance mechanical properties and reduce environmental impacts associated with marble waste disposal. Several researchers have reported that the partial replacement of cement or fine aggregates with WMP leads to improvements in strength characteristics up to an optimum level, after which strength tends to decline.

Waste Glass Powder

Concrete reached its maximum strength at 10% glass powder replacement, with strength declining at greater levels, according to Negim et al. [16], Singh and Jain [17], Tamanna and Tuladhar [18] and Sharma and Sangamnerkar [21]. It's interesting to note that workability improved with more glass powder, but this highlighted the necessity of longer curing times and more evenly distributed particles for effective results at greater dosages.

Glass powder (ground <600 μm) increased strength most dramatically at 20% cement replacement, according to Rehman et al. [19], who attributed the improvement to pozzolanic processes and the creation of more C-S-H gel. In a similar vein, Gautam et al. [22] found that concrete with 20% cement replacement retained high strength without adverse consequences, while glass powder finer than 100 μm showed pozzolanic activity. While highlighting the affordability of WGP, Rohitha and Yeswanth [27] discovered that the compressive and flexural strengths of concrete with 20% glass powder supplementation were comparable to control concrete. Waste glass added up to 20% to rubberized concrete systems improved durability characteristics such as water absorption, shrinkage resistance, and acid resistance while also increasing compressive and tensile strength by 24% and 30%, respectively [42].

The role of particle fineness has been emphasized by multiple researchers. Rehman et al. [19] demonstrated that glass powder below 600 μm enhanced pozzolanic activity. Toro et al. [20],

however, found that substituting cement with glass powder ($d_{50} = 16 \mu\text{m}$) increased air content and reduced density, though consistency remained within fluid concrete limits. This highlights the dual effect of fine glass particles—while improving strength through pozzolanic activity, they may adversely affect fresh properties such as density and air content, while Gautam et al. [22] confirmed similar benefits for particles below $100 \mu\text{m}$.

Glass powder integration has similarly important durability consequences. According to Rehman et al. [19], early alkali consumption of glass particles improved long-term durability by reducing the expansion of the alkali-silica reaction (ASR). Ibrahim [26] also showed that replacing fine aggregate with waste glass up to 40% maintained compressive and tensile strengths, while 15% replacement resulted in a 25% increase in compressive strength and a 37% increase in tensile strength, along with reduced density and improved workability. Spiesz et al. [24] similarly investigated concretes with treated and untreated waste glass, reporting adequate mechanical performance along with enhanced durability, translucency, and air-purifying capacity due to the photocatalytic activity of TiO_2 . Several publications emphasize the benefits of WGP from an environmental and sustainability standpoint [25]. Glass powder makes concrete more economical and ecologically friendly by lowering unit weight, porosity, and water absorption, as demonstrated by Shubham et al. [23]. Its potential for structural applications while supporting environmentally and socially conscious building was highlighted by Batham [28]. Additionally, waste glass was positioned among other industrial by-products by Nilesh et al. [29], indicating its potential as a partial substitute in cementitious systems.

Overall, research demonstrates that when used in appropriate quantities, waste glass powder can improve the mechanical and durability performance of concrete. Maximum compressive strength is frequently reached at 10% cement replacement [16, 18, 21], and compressive, tensile, and flexural characteristics greatly improve with 20% replacement (cement or sand)

[17, 19, 22, 27, 42]. Reductions in strength, density, or workability are commonly observed at greater substitution levels [16, 20]. WGP is still a viable additive for the construction of sustainable concrete, nonetheless.

Waste glass powder (WGP) has been widely investigated as a supplementary cementitious material and fine aggregate replacement in concrete, owing to its pozzolanic activity, availability, and potential for reducing environmental impacts. Several studies indicate that the performance of concrete incorporating WGP depends largely on replacement levels, particle fineness, and curing duration.

Silica Fume and Fly Ash

The deterioration-resistant coefficient of compressive strength, relative dynamic elastic modulus (RDEM), and microstructural evaluation were used to monitor the performance of concretes with w/b ratios of 0.38 and 0.33 that contained fly ash (FA: 10–25% by mass) and silica fume (SF: 5–11%) exposed to freezing-thawing in 5% and 10% Na_2SO_4 . Under 5% Na_2SO_4 , both SF and FA increased resistance to sulfate assault, with SF outperforming FA. The synergistic harm of coupled sulfate and freeze-thaw was highlighted by the notable rise in resistance of plain OPC concrete up to about 125 freeze-thaw cycles, followed by deterioration. Optima were grouped around 5–8% SF and 25% FA [30].

Nanoscale hybridization provides significant synergistic benefits beyond binary SCM systems. Tavakoli and Heidari [31] substituted 5–10% SF and 0.5–1% nano- SiO_2 for cement, indicating a 42.2% increase in compressive strength at 10% SF + 1% nano- SiO_2 compared to control, along with decreased water absorption. These findings corroborate the complimentary functions of SF's microfiller action and ultra-fine, highly reactive silica (filling and pozzolanic effects, nucleation sites), which together refine pore structure and speed up C-S-H formation. In general, the literature supports blended designs by identifying residual products like SF and FA as suitable candidates for cementitious systems [34].

Nguyen and Huynh [37] investigated using incinerator fly ash (IFA) in interlocking concrete bricks (0–60% cement replacement) using a densified mixture design algorithm (DMDA) framework, broadening the waste spectrum. While increasing water absorption and voids, increasing IFA content decreased compressive strength, abrasion resistance, bending strength, and bulk density; SEM showed increasingly less-homogeneous microstructures at higher IFA levels. Despite these drawbacks, DMDA-optimized mixtures satisfied Vietnamese standards, showing that strict particle-packing and proportioning techniques can somewhat mitigate the negative effects of difficult waste streams and provide standard-compliant, sustainability-focused goods [37].

Differential scanning calorimetry showed that blending with Class C FA (10–30%) in sulfate-resisting Portland cement (SRPC) systems accelerated hydration up to four weeks. The presence of calcium sulphoaluminate (CSA) in FA and increased C-S-H from pozzolanic reactions improved early strength and setting [46]. This demonstrates the context-dependent nature of FA's benefits: when combined with a sulfate-resistant clinker and assessed at early ages, FA can function as a chemical and microstructural modifier, enhancing early kinetics in addition to longer-term durability characteristics seen elsewhere [30]. Sustainable self-compacting concrete (SCC) systems that use recycled coarse aggregates (RCA: 50–100%) and high SCM contents (50–75% in binary/ternary/quaternary blends) at the structural-mixture scale show that combining FA, slag, and SF can improve fresh properties (filling ability, passing ability, viscosity, segregation resistance) while compensating for strength penalties caused by RCA. Judicious SCM synergy restores or surpasses compressive strength in comparison to traditional SCC and maximizes sustainability by lowering the demand for cement and virgin aggregate, according to a research of 23 mixes at w/b of 0.35–0.45 [47]. These results connect mixture-scale performance in highly workable concretes with material-scale reactivity (as in [30], [31], [46]).

In parallel, energy-intensive fired clay units are replaced by unburnt CA bricks, which offer a binder-rich route. Bricks were made with different amounts of cement, 60% coal ash, and 10% lime (by weight). In addition to achieving 19 MPa compressive and 2.1 MPa flexural strength, the ideal formulation—10% cement, 10% sand, and 10% quarry dust with 3 s forming—also minimized water absorption and efflorescence and had a lower unit weight than traditional clay bricks. According to a cost comparison, the CA bricks are economical because they save energy during fire and make good use of ash fines [38]. Supplementary cementitious materials (SCMs) have been shown to improve sustainability and durability, especially under linked degradation mechanisms, according to research.

E- Waste

Particle-size bands <10 mm, 10–15 mm, and up to 20 mm were investigated for the partial replacement of natural coarse aggregate with e-waste at a rate of 5–30%. Regardless of particle size, strength gains reverted after 15% and were considered unfeasible for building. In order to produce performance-competitive mixes and divert challenging-to-dispose electronic trash from landfills, the typical stiffness and interfacial transition zone issues associated with polymer-rich e-waste aggregates can be mitigated through controlled gradation and moderation of replacement level.

Pumic

Volcanic pumice is a high-porosity, lightweight aggregate. When volcanic pumice is substituted for aggregate in porous concrete, its inherent vesicular structure increases total porosity and decreases elastic modulus, with only a little decrease in strength when compared to porous mixes using conventional aggregate. Pumice mixes demonstrated potential as impact-energy-absorbing concrete in addition to hydraulic performance, suggesting a market where controlled compliance is beneficial [40]. Although 10–25% pumice enhanced 90-day mechanicals, pumice often decreased early-age strength, validating later-age pozzolanic benefits.

In line with pore refinement, NC (1-3%) significantly increased strength with relatively slight permeability disadvantages. Flexure was significantly enhanced by fibers [41].

Waste foundry sand as a fine aggregate rich in silica. WFS is a reliable partial or complete replacement for fine aggregate in concretes, bricks/blocks, and pavers due to its high SiO₂ concentration and uniform granular gradations from ferrous/non-ferrous casting. Although reported systems exhibit physical, mechanical, microstructural, and durability variations that rely on replacement amount and mixture design, there is a wide range of potential applications, providing a way to reduce the extraction of river sand while increasing the value of a plentiful industrial by-product [50].

Nano technology in Supplementary Cementitious Material:

Nanotechnology has emerged as a transformative field in concrete technology due to its ability to significantly enhance the microstructural, mechanical, and durability properties of cementitious materials. The incorporation of nanomaterials such as nano-silica, nano-alumina, carbon nanotubes (CNTs), and other nanostructured admixtures has shown promising results in improving concrete performance.

Alkali-activated binary concrete (AABC) using natural pozzolan and granulated blast furnace slag demonstrated compressive strengths of up to 43.4 MPa at 360 days, proving that nanoparticle-modified binders can serve as viable alternatives to ordinary Portland cement (OPC) in terms of long-term strength and durability [33]. More broadly, nanotechnology contributes to concrete by improving mechanical properties, thermal stability, corrosion resistance, and even enabling self-healing capabilities, thus extending service life and reducing lifecycle costs [48].

Among various nanomaterials, nano-silica has been the most widely studied due to its ability to refine pore structure and accelerate pozzolanic reactions. Experimental studies confirm that nano-silica, particularly when combined with silica fume and steel fibers, enhances compressive, flexural, and tensile strengths at

both early and later ages. For instance, compressive strength improvements of 40–41% and flexural strength gains of 23–42% were reported across 3–28 days, with SEM micrographs showing denser, more homogeneous microstructures compared to mixes without nano-silica [32]. Similarly, a 10% replacement of cement with nano-silica not only raised compressive strength to 129.48 MPa at 28 days but also improved resistance to sulfate attack, highlighting its role in both strength and durability enhancement [36].

Recent reviews emphasize that nanotechnology can impart multifunctional properties to concrete, such as self-cleaning, self-sensing, and self-compacting behaviors, while also promoting environmental benefits through waste reduction and improved efficiency. However, concerns remain regarding the environmental impacts of large-scale nanoparticle production and the need for safe handling protocols [39].

Nanotechnology applications are not limited to silica-based additives. The use of nanostructured mineral admixtures prepared through high-energy ball milling of industrial byproducts such as spent catalysts, copper slag, and cement kiln dust has also been explored. These materials, when used as partial cement replacements, yielded compressive strength improvements of up to 33% and reduced water absorption by 44%, owing to a denser interfacial transition zone (ITZ) [44][45]. Moreover, nano-modified concretes show potential in geopolymer systems. The addition of nanoparticles contributes to the formation of additional C-S-H, N-A-S-H, and C-A-S-H gels while refining the pore structure, thereby improving the strength and durability of geopolymer composites [43]. Advances in cleaner technologies also point toward integrating CNTs and self-sensing CNT composites into concrete to further improve stiffness, strength, and multifunctionality [35].

Collectively, these studies demonstrate that nanotechnology plays a pivotal role in advancing high-performance and sustainable concretes. While nano-silica remains the most effective and widely used additive, emerging nanomaterials such as alumina nanoparticles, CNTs, and

nanostructured industrial byproducts show great promise. Future work should focus not only on optimizing dosage and dispersion techniques but also on addressing environmental and economic aspects for large-scale applications.

Nano-silica (NS)

Recent advancements in concrete technology highlight nano-silica (NS) as a promising additive for enhancing mechanical performance, durability, and sustainability. Multiple studies have examined NS's effects on concrete properties across varying dosages, binder compositions, and functionalizations, providing a comprehensive understanding of its potential [51–55].

NS improves early-age strength and accelerates hydration due to its high pozzolanic activity and nano-filler effect. For example, incorporating 1% NS into concrete with 30% ground granulated blast-furnace slag (GGBS) increased compressive strength significantly within the first week, while higher dosages (2%) yielded reduced benefits due to agglomeration and limited calcium hydroxide availability. Flexural performance mirrored compressive strength trends, with SEM and RCPT analyses confirming microstructural densification [51]. Hydrophobic NS further enhanced strength but showed mixed results in corrosion resistance due to potential ionic ingress despite improved compactness [52].

NS refines concrete microstructure, reducing porosity and chloride permeability, and improving bond strength at the paste-aggregate interface. Studies using SEM, EDS, and XRD confirm that NS consumes calcium hydroxide and forms additional C-S-H gel, reducing the Ca/Si ratio and creating a denser matrix [54]. Enhanced acid and carbonation resistance has been observed, with NS-modified concretes showing exceptional durability under sulfuric acid exposure. However, NS increases water demand and reduces workability, requiring admixtures to maintain flowability [51, 52].

Literature reviews emphasize that NS performance depends on dosage (commonly 2–3% by cement weight), particle size, purity, and dispersion. Excessive NS can cause agglomeration

and reduced workability, while appropriate dispersion methods, surfactants, and morphological control improve effectiveness. Combining NS with supplementary cementitious materials or fibers can enhance the properties of recycled aggregate concretes and multi-component mixes [53]. Research gaps include the long-term behavior of NS concretes in aggressive environments and at structural scales.

An emerging area is the synthesis of NS from agricultural waste (e.g., rice husk, sugarcane bagasse ash) as an eco-friendly alternative to traditional methods. These approaches reduce environmental impact and support circular economy practices. Techniques such as sol-gel, precipitation, and hydrothermal treatments have produced high-purity NS suitable for construction applications, though process optimization and scale-up remain priorities [55].

Key needs include improving NS dispersion to avoid agglomeration, evaluating rheological behavior, studying fiber-matrix interactions, and assessing NS under thermal, marine, and fire conditions. Integrating NS with other nanomaterials and admixtures may balance workability and strength. Modeling and life-cycle assessments will be critical for mainstream adoption.

Nano-CaCO₃

Research on nano-calcium carbonate (Nano-CaCO₃) in concrete and related composites has grown rapidly, focusing on improving mechanical properties, durability, and sustainability. Studies have evaluated its role as a cementitious additive or partial replacement, often in synergy with waste materials, recycled aggregates, or supplementary cementitious components [56–60].

Nano-CaCO₃ accelerates hydration by providing nucleation sites, forming additional C-S-H gel and carbo-aluminates. It refines pore structures, reduces sorptivity, chloride ingress, and corrosion risk. Dosages of 1–2% typically enhance early-age strength and microstructural density, but higher contents reduce workability and may lower strength due to agglomeration. Setting times decrease with increasing Nano-CaCO₃, requiring

water-reducing admixtures to maintain flowability [57].

When combined with recycled coarse aggregates, Nano- CaCO_3 can partially offset strength losses from aggregate replacement. However, performance depends on dosage and water-to-cement ratio [58].

In ultra-high-performance concretes (UHPC) containing high ceramic tile waste, Nano- CaCO_3 improved workability, shortened setting times, and increased compressive and flexural strengths by up to 38%. It enhanced hydration kinetics, refined ITZ microstructure, and reduced porosity. Sustainability gains included >20% reductions in energy intensity, cost, and CO_2 emissions [59].

Fly Ash and Hybrid Mixes: Nano- CaCO_3 synergizes with fly ash by enhancing early-age hydration and mitigating fly ash's slow strength gain. SEM analyses confirmed filler and seeding effects as key mechanisms [60].

Further exploration of green synthesis and dispersion technologies could broaden Nano- CaCO_3 's use in low-carbon construction.

Carbon-based nano materials

Graphene oxide

Graphene oxide (GO) enhances concrete durability by providing nucleation sites, promoting hydration, and reducing porosity. Studies reported 0.03–0.05% GO as an optimal dosage, achieving refined microstructures resistant to chloride and sulfate ingress. Improvements include up to 50% reduction in chloride permeability. However, dispersion and stability in alkaline environments remain challenges, requiring further investigation and field-scale trials for commercialization [61].

Incorporating rGO into waste-based concrete with high levels of GGBS, fly ash, lead smelter slag, and recycled aggregates mitigates strength losses common in such mixes. At 0.1% rGO, compressive, tensile, and flexural strengths improved by 42–47%, while water absorption and shrinkage decreased by 35–45%. Microstructural analysis confirmed reduced porosity and enhanced hydration products. However, workability decreased due to rGO's

high surface area, and agglomeration at higher dosages (0.3%) limited benefits. Dispersion and cost remain barriers to large-scale adoption [62].

Environmental analysis revealed reduced embodied CO_2 ($\text{EI} = 5.37 \text{ kgCO}_2/\text{MPa}$ vs. 6.62 for control). Field validation and cradle-to-grave assessments are needed to confirm long-term environmental gains [63]. Thermal conductivity decreased by 33% at higher GO levels, suggesting thermal insulation benefits. XRD confirmed GO's compatibility with geopolymeric matrices, supporting its potential for sustainable infrastructure using industrial by-products [64].

Performance strongly depends on GO properties, superplasticizer type, and dispersion methods. GO-B (smaller particle size, higher functional groups) outperformed GO-A. Ultrasonic mixing combined with polycarboxylate-based superplasticizers yielded the best results, achieving up to 33% improvement in compressive strength and 24–30% increases in tensile, flexural, and modulus values [65].

Future studies should target scalable dispersion technologies, cost-effective synthesis, field trials under harsh conditions, and integration with sustainable binders and aggregates. Broader life-cycle and durability studies are critical to realizing GO's potential in sustainable, high-performance cementitious systems.

Carbon nano tubes (CNTs)

Recent studies have highlighted the significant potential of carbon nanotube-enhanced green concrete in addressing environmental and performance-related challenges in the construction industry. In particular, the addition of 0.1% CNTs reduced sorptivity by 28.76%, sulphate-induced mass and compressive strength losses by 50.93% and 48.47%, respectively, and acid attack mass loss by 35.97%, confirming the synergistic effect of CNT filling, bridging action, and RHA pozzolanic reactions in densifying the concrete microstructure [67]. Complementary studies on carbon nanotube concrete also emphasized that CNTs, including both single-walled and multi-walled variants, significantly improve compressive, tensile, and flexural strength, fracture toughness, abrasion resistance,

permeability resistance, and self-sensing capabilities even at very low dosages. Owing to their exceptional tensile strength, corrosion resistance, thermal stability, and crack-bridging ability, CNTs are increasingly recognized as promising nano materials for producing high-strength, durable, and sustainable concrete for future construction applications [68].

Carbon nano fibers (CNFs)

Carbon nanofibers (CNFs) have demonstrated significant improvements in the mechanical performance and durability of concrete due to their nano-scale crack-bridging and pore-filling abilities. Studies reported that the incorporation of CNFs enhanced compressive strength, flexural strength, fracture toughness, chloride penetration resistance, and freeze-thaw durability. An optimal CNF dosage of approximately 0.1–0.5% was found to effectively reduce porosity and permeability while densifying the calcium silicate hydrate (C-S-H) matrix. For example, CNFs reduced concrete porosity by 9.0 wt.% and water permeability by 39.3%, thereby improving resistance to environmental deterioration [69,71,75]. Hybrid CNF systems combined with polyvinyl alcohol fibers further enhanced chloride ion resistance and mechanical behavior through synergistic reinforcement mechanisms [71]. Moreover, CNFs improved fire endurance and crack resistance in high-strength concrete exposed to elevated temperatures up to 800 °C by effectively bridging microcracks and limiting structural degradation [69]. Microstructural investigations using SEM, MIP, and EDS confirmed that CNFs refine pore structure, reduce microcracking, and strengthen the interfacial transition zone within cementitious composites [73,75].

Nano-titanium dioxide (Nano-TiO₂)

Nano-titanium dioxide (Nano-TiO₂) has been widely investigated for its photocatalytic, self-cleaning, and mechanical enhancement properties in concrete. Research indicates that Nano-TiO₂ improves hydration reactions, refines pore structure, and increases compressive and flexural strengths while simultaneously imparting

self-cleaning and air-purifying capabilities. The photocatalytic activity of Nano-TiO₂ enables degradation of pollutants such as NO_x and organic contaminants when exposed to sunlight, making it suitable for sustainable urban infrastructure [70,72]. Studies showed that appropriate Nano-TiO₂ particle size and dosage significantly improved hardened concrete properties, reduced permeability, and enhanced durability while maintaining acceptable workability [72,74]. Additionally, Nano-TiO₂ contributes to denser microstructures by accelerating cement hydration and promoting the formation of additional C-S-H gel, which improves resistance against chloride penetration, carbonation, and surface contamination [73,74]. These characteristics make Nano-TiO₂ concrete highly suitable for environmentally friendly and low-maintenance construction applications [70,74].

Nano-magnesium oxide (Nano-MgO)

Nano-magnesium oxide (Nano-MgO) has emerged as an effective nano-additive for improving shrinkage resistance, durability, and mechanical performance in cement-based materials. Research has shown that Nano-MgO contributes to expansive hydration products, which compensate for shrinkage and reduce crack formation in concrete. The addition of Nano-MgO enhances compressive strength, refines pore structure, and improves resistance to sulphate attack, chloride ingress, and carbonation by densifying the cement matrix [73,76]. Nano-MgO particles also accelerate cement hydration and promote the formation of magnesium silicate hydrate (M-S-H) gel, which contributes to improved long-term durability and dimensional stability [74]. Furthermore, studies have highlighted the effectiveness of Nano-MgO in mitigating autogenous and drying shrinkage, especially in high-performance and self-compacting concretes, thereby enhancing structural longevity and sustainability in aggressive environmental conditions [76, 77].

Conclusion

The concrete structures prepared from the waste materials have lower environmental impact through reduced CO₂ emission and maintain all the specification of "Green Concrete". The significance of this study is to encourage the usage of solid waste to minimize the disposal cost of waste materials, decrease the environmental risk of pollution and save the landfill space.

Industrial waste material like fly ash, silica fume, waste glass, waste marble powder, e waste and pumic can be added in concrete as cement and sand and aggregate substitution. the optimum dogaes varies however mostly wate material gives results under 30% replacement. Compressive strength , tensile strength, flexural strength increases densifying the microstructure and increasing the resistivity against weather and water. Nano science is the science of studying, controlling, and re-engineering of particles at the atomic and molecular level. The size of the particles is the main reason for using this science as the material's properties are highly altered under a Nano scale. Nanoparticles can be in the form of a powder, fibre, crystal, or pipe. It can be used as it is or can be deployed to reach the desired characteristics. Nano materials like nano silica, carbon nano tubes, graphene oxide, nano fibers, nano titanium oxide, nano magnesium oxide demonstrated significant improvements in the mechanical performance and durability of concrete due to their nano-scale crack-bridging and pore-filling abilities. Studies reported that the incorporation of nano materials enhanced compressive strength, flexural strength, fracture toughness, chloride penetration resistance, and freeze-thaw durability. Self-compacting concrete flow ability, passing ability, and viscosity declined as the NS, NWG, and NWC increased optimum dosage of nano materials is .1%.Waste-milled nano materials are comparable to nano-silica, which is chemically prepared to improve SCC mechanical properties and purify the microstructure. However the dispersion method becomes critical and necessity of adding super plasticizers or water reducers is ensured as the finer particles agglomerates in concrete making weak zones. So further studies should be done on

dispersion methods, aggressive environment exposure, long term durability of these waste materials

Acknowledgement

Authors feel heartfelt gratitude to department of technology university of Lahore for their support.

Conflict of interest

Author has no conflict of interest.

References

- [1] Kishan N et al ,2017, A Review on Utilization of Marble Waste Powder as a Partial Replacement of Cement in Glasscrete Concrete, International Journal of Advance Engineering and Research Development Volume 4, Issue 11,
- [2] Bassam A. Tayeh ,2018, Effects of marble, timber, and glass powder as partial replacements for cement
- [3] Hassani, A., H. Ganjidoust, and A.A. Maghanaki, Use of plastic waste (poly-ethylene terephthalate) in asphalt concrete mixture as aggregate replacement. Waste Management & Research, 2005. 23(4): p. 322-327.
- [4] Aneel Manan et al, 2025, " Utilizing waste materials in concrete: a review on mechanical and sustainable performance", Green Materials,2025, ISSN 2049-1239,
- [5] Rai, B., et al., Influence of Waste marble powder /granules in Concrete mix. International journal of civil and structural engineering, 2011. 1(4): p. 827.
- [6] Garas, G., Sayed, A. M., & Bakhoun, E. S. H. (2021). Application of nano waste particles in concrete for sustainable construction: a comparative study. *International Journal of Sustainable Engineering*, 14(6), 2041-2047. <https://doi.org/10.1080/19397038.2021.1963004>
- [7] Reham M. Hussien et al , 2022, "Influence of nano waste materials on the mechanical properties, microstructure, and corrosion resistance of self-compacted concrete" ,Case Studies in Construction Materials, Volume 16,ISSN 2214-5095,

- [8] Sonu Pal et al,2016, Effects of Partial Replacement of Cement with Marble Dust Powder on Properties of Concrete, IJIRST -International Journal for Innovative Research in Science & Technology| Volume 3 | Issue 03 | August 2016 ISSN (online): 2349-6010
- [9] Messaouda Belouadah et al ,2019, Influence of the addition of glass powder and waste marble powder on the physical and mechanical behavior of composite cement, 3rd World Conference on Technology, Innovation and Entrepreneurship (WOCTINE)
- [10] Sahil Patial, Prince Sharma (2020) A Review Paper on Effect of Marble Dust Powder and Quartzite Dust Powder on Strength Characteristics of Concrete International Research Journal of Engineering and Technology (IRJET) e-ISSN: 2395-0056 Volume: 07 Issue: 12 p-ISSN: 2395-0072 © 2020 Page 877
- [11] Tavakoli, Davoud & Hashempour, Masoumeh & Heidari, Ali. (2018). Use of waste materials in concrete: A review. Pertanika Journal of Science and Technology. 26. 499-522.
- [12] Abdul Ghani1, Zeeshan Ali, Fasih Ahmed Khan, Said Rehan Shah(2020) Experimental study on the behavior of waste marble powder as partial replacement of sand in concrete · Published online: Springer Nature Switzerland AG 2020
- [13] O M Ofuyatan et al (2019) Utilization of marble dust powder in concrete, 1st International Conference on Sustainable Infrastructural Development IOP Conf. Series: Materials Science and Engineering 640 (2019) 012053 IOP Publishing doi:10.1088/1757-899X/640/1/012053
- [14] Oumaima, Bourzik & Baba, Khadija & Akkouri, Nacer & Nounah, Abderrahmane. (2022). Effect of waste marble powder on the properties of concrete. Materials Today: Proceedings. 72. 10.1016/j.matpr.2022.07.184.
- [15] Tewodros Getachew , Miskir Gebrehiwot, Investigation on Partial Replacement of Cement with Marble Dust Powder on C-25 Concrete Production in Benishangul Gumuz; Ethiopia , International Journal of Construction Engineering and Management 2020, 9(4): 126-133 DOI: 10.5923/j.ijcem.20200904.03
- [16] E.M. Negim et al ,2012, Glass Powder Utilisation in Concrete Production, European Journal of Applied Sciences 4 (4): 173-176, 2012 ISSN 2079-2077 © IDOSI Publications, 2012 DOI: 10.5829/idosi.ejas.2012.4.4.1102
- [17] Bhupinderjeet Singh and Ritesh Jain ,2018, Use of waste glass in concrete: A review, Advances in Agriculture and Natural Sciences for Sustainable Agriculture, (Special Issue- 5), E-ISSN: 2278-4136 P-ISSN: 2349-8234 JPP 2018; SP5: 96-99
- [18] Nafisa Tamanna1, and Rabin Tuladhar ,2020, Sustainable Use of Recycled Glass Powder as Cement Replacement in Concrete, The Open Waste Management Journal Content list available at: <https://openwastemanagementjournal.com> RESEARCH ARTICLE
- [19] Hamdule Abdul Rehman et al,2021, Use of Glass Powder as Partial Replacement of Cement in Cement Concrete , International Journal of Engineering Research & Technology (IJERT) ISSN: 2278-0181 Published by, www.ijert.org NREST - 2021 Conference Proceeding
- [20] Eva M. García del Toro , Daniel Alcalá-Gonzalez , María Isabel Más-López , Sara García-Salgado and Santiago Pindado,2021, applied sciences Article Use of Ecofriendly Glass Powder Concrete in Construction of Wind Farms, <https://doi.org/10.3390/app11073050>
- [21] Ashutosh Sharma, Ashutosh Sangamnerkar ,2015, Glass Powder – A Partial Replacement for Cement, International Journal of Core Engineering & Management (IJCEM) Volume 1, Issue 11

- [22] Shyamji Gautam, Abhishek Kumar, Mohd. Afaq, 2016, A Review Report On Comparative Study of Waste Glass Powder as Pozzolanic Material in Concrete, International Research Journal of Engineering and Technology (IRJET) e-ISSN: 2395-0056 Volume: 03 Issue: 03 | Mar-2016 www.irjet.net p-ISSN: 2395-0072 © 2016, IRJET | Impact Factor value: 4.45 | ISO 9001:2008 Certified Journal | Page 500
- [23] Shubham G. Keshattiwar, Siddharth S. Tode, Shubham M. Menewar, Girish V. Mahalle, Akshay H. Shirbhate, Akshay Khadse, Aishwarya H. Meshram, 2019, Partial Replacement of PPC with Glass powder, IOSR Journal of Engineering (IOSRJEN) www.iosrjen.org ISSN (e): 2250-3021, ISSN (p): 2278-8719 PP 17-24 International Conference on Innovation & Research in Engineering, Science & Technology 17 | Page (ICIREST-19)
- [24] P. Spiesz a,b,†, S. Rouvas a, H.J.H. Brouwers, 2016, Utilization of waste glass in translucent and photocatalytic concrete, Construction and Building Materials journal homepage: www.elsevier.com/locate/conbuildmat
- [25] Ahmad, Soran & Rafiq, Serwan & Abdullah, Wrya & Pour, Amir. (2024). Effects of using powdered waste glass as cement replacement on the fresh and mechanical properties of concrete: A review. 020051. 10.1063/5.0205664.
- [26] K. I. M. Ibrahim, 2017, The Effect of Using Waste Glass [WG] as Partial Replacement of sand on Concrete, IOSR Journal of Mechanical and Civil Engineering (IOSR-JMCE) e-ISSN: 2278-1684, p-ISSN: 2320-334X, Volume 14, Issue 2 Ver. II (Mar. - Apr. 2017), PP 41-45 www.iosrjournals.org
- [27] Rohitha.B1, Yeswanth Sai.T2, 2020, A Literature Study Paper On Sustainable Concrete Using Recycled Glass Mortar, International Research Journal of Engineering and Technology (IRJET) e-ISSN: 2395-0056 Volume: 07 Issue: 05, ISSN: 2395-0072
- [28] Geeta Batham et al, 2020, Cement Concrete using Industrial Waste (Glass Powder): A Review, International Research Journal of Engineering and Technology (IRJET) e-ISSN: 2395-0056 Volume: 07 Issue: 04, p-ISSN: 2395-0072
- [29] Nilesh K et al, 2015, "Utilization of Various Waste Materials in Concrete a Literature Review", International Journal of Engineering Research & Technology (IJERT), ISSN: 2278-0181
- [30] Dezhi Wang et al 2017, Durability of concrete containing fly ash and silica fume against combined freezing-thawing and sulfate attack, Construction and Building Materials 147:398-406, DOI:10.1016/j.conbuildmat.2017.04.172
- [31] Davoud Tavakoli, Ali Heidari, 2013, Properties of concrete incorporating silica fume and nano-SiO₂, Indian Journal of Science and Technology 6(1):3946-3950 DOI:10.17485/ijst/2013/v6i1.12
- [32] Ola Adel Qasim and Suha Adel Al-Ani, 2020, Effect of Nano-Silica Silica Fume and Steel Fiber on the Mechanical Properties of Concrete at Different Ages Civil Engineering Department, Al-Mansour University College, Baghdad, Iraq
- [33] a, R. Mejía de Gutiérrez, F. Puertasb, 2019, Materiales de Construcción Alkali-activated binary concrete based on a natural pozzolan: physical, mechanical and microstructural characterization, Vol. 69, Issue 335, e191 ISSN-L: 0465-2746 <https://doi.org/10.3989/mc.2019.06618>
- [34] Agarwal, Neeraj & garg, nikhil. (2018). A Research on Green Concrete, IJIRMPs | Volume 6, Issue 4
- [35] Bambang Suhendro, Toward 2014, Green Concrete for Better Sustainable Environment, Procedia Engineering, Volume 95, Pages 305-320, ISSN 1877-7058, <https://doi.org/10.1016/j.proeng.2014.12.190>.
- [36] Saloma, Amrinsyah Nasution, Iswandi Imran, Mikrajuddin Abdullah,

- Improvement of Concrete Durability by Nanomaterials, *Procedia Engineering*, Volume 125, 2015, Pages 608-612, ISSN 1877-7058, <https://doi.org/10.1016/j.proeng.2015.11.078>. (<https://www.sciencedirect.com/science/article/pii/S1877705815033950>)
- [37] Vishwakarma, Vinita. (2018). Green Concrete mix using solid waste and nanoparticles as alternatives – A review.
- [38] Nguyen, Huu May & Huynh, Trong-Phuoc. (2022). Turning incinerator waste fly ash into interlocking concrete bricks for sustainable development. *Construction and Building Materials*. 321. 126385. 10.1016/j.conbuildmat.2022.126385.
- [39] Mukhtar, Ahmad & Qazi, Asad & Khan, Qasim & Munir, Muhammad & Kazmi, Syed & Hameed, Asif. (2022). Feasibility of Using Coal Ash for the Production of Sustainable Bricks. *Sustainability*. 14. 6692. 10.3390/su14116692.
- [40] Hariyadia, Hiroki Tamai, 2015, Enhancing the performance of porous concrete by utilizing the pumice aggregate, The 5th International Conference of Euro Asia Civil Engineering Forum (EACEF-5), *Procedia Engineering* 125 (2015) 732 – 738, Available online at www.sciencedirect.com
- [41] Mehrabi, Peyman & Shariati, Mahdi & Kabirifar, Kamyar & Jarrah, Majid & Rasekh, Haleh & Nguyen-Thoi, Trung & Shariati, Ali & Jahandari, Soheil. (2021). Effect of pumice powder and nano-clay on the strength and permeability of fiber-reinforced pervious concrete incorporating recycled concrete aggregate. *Construction and Building Materials*. 287. 10.1016/j.conbuildmat.2021.122652.
- [42] Ahmad, Jawad & Zhou, Zhiguang & Martínez García, Rebeca & Abbas, Nadeem. (2022). A study on the microstructure and durability performance of rubberized concrete with waste glass as binding material. *Journal of Building Engineering*. 49. 104054. 10.1016/j.job.2022.104054.
- [43] Ahmed, Hemn & Mohammed, Azad & Mohammed, Ahmed. (2022). The role of nanomaterials in geopolymer concrete composites: A state-of-the-art review. *Journal of Building Engineering*. 49. 10.1016/j.job.2022.104062.
- [44] Al-Jabri, K., & Shoukry, H. (2014). Use of nano-structured waste materials for improving mechanical, physical and structural properties of cement mortar. *Construction and Building Materials*, 73, 636-644. <https://doi.org/10.1016/j.conbuildmat.2014.10.004>
- [45] Mehdizadeh Miyandehi, Bahareh & Jahandari, Soheil & Vessalas, Kirk & Miraki, Hania & Rasekh, Haleh & Samali, Bijan. (2021). Fresh, Mechanical, and Durability Properties of Self-Compacting Mortar Incorporating Alumina Nanoparticles and Rice Husk Ash. *Materials*. 14. 6778. 10.3390/ma14226778
- [46] P. Ilayabarathi ., S. Kannan., R Vijayabalan and S. Barathan, 2011, A study on hydration of fly ash blended sulphate resisting portland (type v) cement using differential scanning calorimetry, *International Journal of Recent Scientific Research* Vol. 2, Issue, 1, pp. 18-21, ISSN: 0976-303
- [47] Zhanggen Guo, Jing Zhang, Tao Jiang, Tianxun Jiang, Chen Chen, Rui Bo & Yan Sun (2022) Development of sustainable self-compacting concrete using recycled concrete aggregate and fly ash, slag, silica fume, *European Journal of Environmental and Civil Engineering*, 26:4, 1453-1474, DOI: 10.1080/19648189.2020.1715847

- [48] Costa, Vitor & Souza Jr, Fernando & Thomas, Sabu & Toledo Filho, Romildo & Sousa, Luana & Thode, Sérgio & Carvalho, Fernanda & Maranhão, Fabíola & Aboelkheir, Mostafa & Lima, Nathali & Pereira, Emiliane & Hasparyk, N.. (2021). Nanotechnology in Concrete: a Bibliometric Review. *Brazilian Journal of Experimental Design, Data Analysis and Inferential Statistics*. 1. 100-113. 10.29327/232092.1.1-14.
- [49] Faleschini, Flora & Marzi, Paola & Pellegrino, Carlo. (2014). Recycled concrete containing EAF slag: Environmental assessment through LCA. *European Journal of Environmental and Civil Engineering*. 18. 10.1080/19648189.2014.922505.
- [50] Atish Bhardwaj, Pankaj Kumar, Salman Siddique & Abhilash Shukla (2022) Comprehensive review on utilization of waste foundry sand in concrete, *European Journal of Environmental and Civil Engineering*, DOI: 10.1080/19648189.2022.2070778
- [51] Alqamish, H. H., & Al-Tamimi, A. K. (2021). Development and Evaluation of Nano-Silica Sustainable Concrete. *Applied Sciences*, 11(7), 3041. <https://doi.org/10.3390/app11073041>
- [52] Alvansazyazdi, M., Alvarez-Rea, F., Pinto-Montoya, J., Khorami, M., Bonilla-Valladares, P. M., Debut, A., & Feizbahr, M. (2023). Evaluating the Influence of Hydrophobic Nano-Silica on Cement Mixtures for Corrosion-Resistant Concrete in Green Building and Sustainable Urban Development. *Sustainability*, 15(21), 15311. <https://doi.org/10.3390/su152115311>
- [53] Hamada, H., Shi, J., Yousif, S. T., Al Jawahery, M., Tayeh, B., & Jokhio, G. (2023). Use of nano-silica in cement-based materials – a comprehensive review. *Journal of Sustainable Cement-Based Materials*, 12(10), 1286–1306. <https://doi.org/10.1080/21650373.2023.2214146>
- [54] Kashyap, V.S., Sancheti, G., Yadav, J.S. et al. Smart sustainable concrete: enhancing the strength and durability with nano silica. *Smart Constr. Sustain. Cities* 1, 20 (2023). <https://doi.org/10.1007/s44268-023-00023-1>
- [55] Yaqueen, M.N., Kuity, A. & Ahmed, M.A. Sustainable Nano Silica Production from Agricultural Residues: A Review of Green Synthesis Techniques and Performance in Asphalt Applications. *Int. J. Pavement Res. Technol.* (2025). <https://doi.org/10.1007/s42947-025-00585-6>
- [56] Sldozian, R.J.A., Hamad, A.J. & Al-Rawe, H.S. Mechanical properties of lightweight green concrete including nano calcium carbonate. *J Build Rehabil* 8, 3 (2023). <https://doi.org/10.1007/s41024-022-00247-1>
- [57] Sharma, H., & Ashish, D. K. (2023). Nano CaCO₃ for enhancing properties of cement-based materials: a comprehensive review. *Journal of Sustainable Cement-Based Materials*, 12(12), 1475–1494. <https://doi.org/10.1080/21650373.2023.2233512>
- [58] Yousheng, D., Keqin, Z., Yunbo, F. et al. Analysis and optimization of design parameters for recycled concrete modified with nano-CaCO₃ considering environmental and economic and mechanical properties. *J Mater Cycles Waste Manag* 25, 3651–3663 (2023). <https://doi.org/10.1007/s10163-023-01785-7>
- [59] Zhang, Liqing, Bian, Mingqiang, Xiao, Zhenrong, Wang, Yunyang, Xu, Kaicheng, Han, Baoguo and Huang, Hong. "Using nano-CaCO₃ and ceramic tile waste to design low-carbon ultra high performance concrete" *Nanotechnology Reviews*, vol. 13, no. 1, 2024, pp. 20230198. <https://doi.org/10.1515/ntrev-2023-0198>

- [60] Sun, Yanqun, Zhang, Peng, Guo, Weina, Bao, Jiuwen, Qu, Chengping, Effect of Nano- CaCO_3 on the Mechanical Properties and Durability of Concrete Incorporating Fly Ash, *Advances in Materials Science and Engineering*, 2020, 7365862, 10 pages, 2020. <https://doi.org/10.1155/2020/7365862>
- [61] Udumulla, D., Ginigaddara, T., Jayasinghe, T., Mendis, P., & Baduge, S. (2024). Effect of Graphene Oxide Nanomaterials on the Durability of Concrete: A Review on Mechanisms, Provisions, Challenges, and Future Prospects. *Materials*, 17(10), 2411. <https://doi.org/10.3390/ma17102411>
- [62] Mohammad Valizadeh Kiamahalleh, Aliakbar Gholampour, Youhong Tang, Tuan D. Ngo, 2024, "Incorporation of reduced graphene oxide in waste-based concrete including lead smelter slag and recycled coarse aggregate", *Journal of Building Engineering*, Volume 88, 109221, ISSN 2352-7102, <https://doi.org/10.1016/j.jobbe.2024.109221>.
- [63] Ginigaddara, T., Devapura, P., Vimonsatit, V., Booy, M., Mendis, P., & Satsangi, R. (2025). A Comprehensive Study of the Macro-Scale Performance of Graphene Oxide Enhanced Low Carbon Concrete. *Construction Materials*, 5(3), 47. <https://doi.org/10.3390/constrmater5030047>
- [64] Maglad, A. M., Zaid, O., Arbili, M. M., Ascensão, G., Șerbănoiu, A. A., Grădinaru, C. M., García, R. M., Qaidi, S. M. A., Althoe, F., & de Prado-Gil, J. (2022). A Study on the Properties of Geopolymer Concrete Modified with Nano Graphene Oxide. *Buildings*, 12(8), 1066. <https://doi.org/10.3390/buildings12081066>
- [65] Isuri Fonseka et al, 2024, "Influence of graphene oxide properties, superplasticiser type, and dispersion technique on mechanical performance of graphene oxide-added concrete", *Construction and Building Materials*, Volume 428, 136415, ISSN 0950-0618, <https://doi.org/10.1016/j.conbuildmat.2024.136415>.
- [66] Kai Cui et al, 2023, "Understanding the role of carbon nanotubes in low-carbon concrete: From experiment to molecular dynamics, *Cement and Concrete Composites*", Volume 142, 105189, ISSN 0958-9465, <https://doi.org/10.1016/j.cemconcomp.2023.105189>.
- [67] Jing, Y., Lee, J.C., Moon, W.C. et al. "Durability and environmental evaluation of rice husk ash sustainable concrete containing carbon nanotubes". *Sci Rep* 15, 4352 (2025). <https://doi.org/10.1038/s41598-025-88927-z>
- [68] Breetha Yesudhas Jayakumari et al, 2023, "A review on characteristics studies on carbon nanotubes-based cement concrete", *Construction and Building Materials*, Volume 367, 130344, ISSN 0950-0618, <https://doi.org/10.1016/j.conbuildmat.2023.130344>
- [69] Afzal, M. T., & Khushnood, R. A. (2021). Influence of carbon nano fibers (CNF) on the performance of high strength concrete exposed to elevated temperatures. *Construction and Building Materials*, 268, 121108. <https://doi.org/10.1016/j.conbuildmat.2020.121108>
- [70] Lee, J. W., Lee, S. H., Jang, Y. I., & Park, H. M. (2021). Evaluation of reducing NO and SO_2 concentration in nano $\text{SiO}_2\text{-TiO}_2$ photocatalytic concrete blocks. *Materials*, 14(23), 7182. <https://doi.org/10.3390/ma14237182>
- [71] Meng, W., & Khayat, K. H. (2016). Mechanical properties of ultra-high-performance concrete enhanced with graphite nanoplatelets and carbon nanofibers. *Composites Part B: Engineering*, 107, 113–122. <https://doi.org/10.1016/j.compositesb.2016.09.069>

- [72] Ren, J., Lai, Y., & Gao, J. (2018). Exploring the influence of SiO_2 and TiO_2 nanoparticles on the mechanical properties of concrete. *Construction and Building Materials*, 175, 277–285. <https://doi.org/10.1016/j.conbuildmat.2018.04.181>
- [73] Shah, S. P., Hou, P., & Konsta-Gdoutos, M. S. (2015). Nano-modification of cementitious material: Toward a stronger and durable concrete. *Cement and Concrete Composites*, 61, 1–11. <https://doi.org/10.1016/j.cemconcomp.2015.04.009>
- [74] Sikora, P., Cendrowski, K., Markowska-Szczupak, A., Horszczaruk, E., & Mijowska, E. (2022). Influence of nano- TiO_2 , nano- Fe_2O_3 , nanoclay and nano- CaCO_3 on the properties of cement/geopolymer concrete. *Cleaner Materials*, 4, 100061. <https://doi.org/10.1016/j.clema.2022.100061>
- [75] Wang, T., et al. (2020). Experimental study on the effect of carbon nanofiber content on the durability of concrete. *Construction and Building Materials*, 250, 118891. <https://doi.org/10.1016/j.conbuildmat.2020.118891>
- [76] Zhu, W., Bartos, P. J. M., & Porro, A. (2004). Application of nanotechnology in construction: Summary of a state-of-the-art report. *Materials and Structures*, 37(9), 649–658.
- [77] Zyka, J., & Mohammed, B. S. (2014). State-of-the-art report on use of nano-materials in concrete. *International Journal of Pavement Engineering*, 15(10), 940–949. <https://doi.org/10.1080/10298436.2014.893327>